

ECLIPSE® FLOOR 200

Shrinkage reducing admixture

Product Description



Eclipse® Floor 200 is a liquid admixture for concrete that dramatically reduces drying shrinkage and the potential for drying shrinkage-induced cracking and curling. Rather than

functioning as an expansive agent, Eclipse Floor 200 acts by reducing the surface tension of pore water. Eclipse Floor 200 is specifically formulated for use in non air-entrained applications only, such as interior slab-on-grade construction. Eclipse Floor 200 is a clear liquid admixture that weighs approximately 7.7 lbs/gal (0.92 kg/L).

Uses

Eclipse Floor 200 may be used in any concrete but provides the most value when used for interior slab-on-grade construction where the potential for cracking and curling due to drying shrinkage is prevalent and undesirable. Other potential Eclipse Floor 200 applications in non air-entrained concrete mixes not subjected to freeze-thaw cycling include bridge decks, parking garages, marine structures and containment structures. Eclipse Floor 200 can be used in ready mix, precast, and prestress non air-entrained concrete, in addition to mortar, grout and wet mix shotcrete.

Performance

Impact on plastic and hardened concrete properties—

Figure 1 illustrates ASTM C157 drying shrinkage reduction up to 90 days (7 day wet cure) for concrete mixtures containing 0.75 gal/yd³ (3.7 L/m³) and 1.5 gal/yd³ (7.4 L/m³) of Eclipse Floor 200. This data represents typical Eclipse Floor 200 test results for a well proportioned concrete mixture. However, it is recommended that pre-job drying shrinkage testing be conducted to determine actual drying shrinkage reduction for a specific mix proportion and set of materials.

In properly designed low shrinkage concrete mixtures for slab on grade construction, the inclusion of Eclipse Floor 200 may enable joint spacings of up to 50 feet (15 meters) or beyond. The use of Eclipse Floor 200 results in an overall higher value flooring system including:

- Lower joint maintenance cost due to minimum joint openings at a given joint spacing or fewer joints at extended joint spacing.
- Flatter surfaces due to curling reduction
- Longer surface life

Product Advantages

- Reduces drying shrinkage up to 80% at 28 days and 50% at 1 year and beyond
- Reduces the potential of cracking due to drying shrinkage in fully and partially restrained concrete
- Reduces curling
- Improves durability, which reduces maintenance and repair costs



Eclipse Floor 200 impacts workability (slump) similarly to an equal volume of water; therefore Eclipse Floor 200 should be used as a replacement for an equal volume of water. Eclipse Floor 200 may have a slight retarding effect on a concrete mix, typically less than one hour. In mixtures containing mid- or high-range water reducers, it is recommended Eclipse Floor 200 be used with near neutral setting polycarboxylate-based admixtures (including the MIRA® and ADVA® product lines). Eclipse Floor 200 may also cause a slight (typically less than 10%) decrease in early and later age compressive strengths. Eclipse Floor 200 is a non-chloride containing, non-corrosive admixture that will not initiate or contribute to the corrosion of reinforcing steel.

Addition Rates

Typical Eclipse Floor 200 dosage rates are 0.5 to 1.5 gal/yd³ (2.5 to 7.5 L/m³). However, dosage rates ranging from 0.2 to 2.0 gal/yd³ (1.0 to 10 L/m³) can be utilized to meet specific drying shrinkage requirements. Dosage rates as low as 0.2 gal/yd³ (1.0 L/m³) have been successfully used in concrete mixes that are just outside drying shrinkage specifications. Although shrinkage reduction as a function of dosage rate is fairly linear, it is recommended that trial mixtures be evaluated for shrinkage reduction in accordance with ASTM C157 prior to construction.

Compatibility with Other Admixtures and Batch Sequencing

Eclipse Floor 200 is fully compatible with the complete line of Grace Admixtures. In mixtures containing mid- or high-range water reducers, it is recommended that Eclipse Floor 200 be used with polycarboxylate based MIRA mid-range water reducers and ADVA high-range water reducers. In general, Eclipse Floor 200 may be added to the concrete batch sequencing at any time, however preferably after the dry materials and most of the water. Different sequencing may be used if local testing shows better performance. Please see Grace Technical Bulletin TB-0110, *Admixture Dispenser Discharge Line Location and*

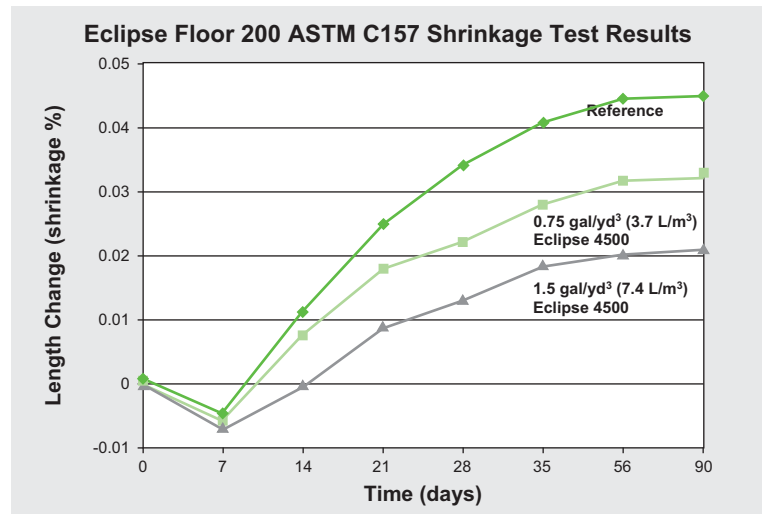


Figure 1

Sequencing for Concrete Batching Operations for further recommendations. Eclipse Floor 200 should not come in contact with any other admixture before or during the batching process, even if diluted in mix water. Pretesting of the concrete mix should be performed before use, and as conditions and materials change in order to assure compatibility, and to optimize dosage rates, addition times in the batch sequencing and concrete performance. Please consult your Grace representative for specific guidance.

Packaging & Handling

Eclipse Floor 200 is currently available in bulk quantities by Grace metered systems, in 275 gal (1,040 L) totes, or in 55 gal (208 L) drums.

Dispensing Equipment

A complete line of automatic dispensing equipment is available through W.R. Grace & Co.–Conn.

Flammability

Eclipse Floor 200 has a flash point of 216°F (102°C). This is substantially above the upper limit of 140°F (60°C) for classification as a flammable material and above the limit of 200°F (93°C) for classification as a combustible material by DOT requirements. Nonetheless, this product must be treated with care and protected from excessive heat, open flame or sparks. For more information, consult the MSDS.

www.graceconstruction.com

North American Customer Service: 1-877-4AD-MIX1 (1-877-423-6491)

Eclipse, the Eclipse logo, MIRA and ADVA are trademarks of W. R. Grace & Co.–Conn. registered in the United States and other countries.

We hope the information here will be helpful. It is based on data and knowledge considered to be true and accurate and is offered for the users' consideration, investigation and verification, but we do not warrant the results to be obtained. Please read all statements, recommendations or suggestions in conjunction with our conditions of sale, which apply to all goods supplied by us. No statement, recommendation or suggestion is intended for any use which would infringe any patent or copyright. W. R. Grace & Co.–Conn., 62 Whittemore Avenue, Cambridge, MA 02140. In Canada, Grace Canada, Inc., 294 Clements Road, West, Ajax, Ontario, Canada L1S 3C6.

This product may be covered by patents or patents pending.
EC-21B Printed in U.S.A. 12/09

Copyright 2009. W. R. Grace & Co.–Conn.
FA/DSG/1M

GRACE